


Version: 1.0
Last update: 11-12-2024

Technical datasheet

Prusament PETG Magnetite 40% by Prusa Polymers

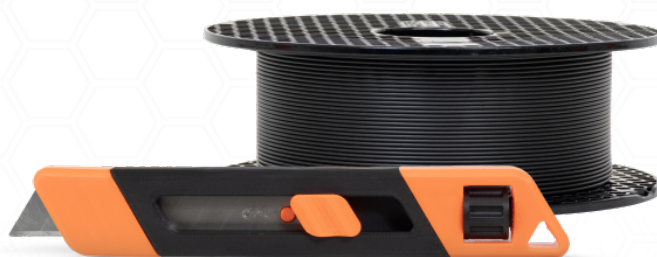

Identification

Trade Name	Prusament PETG Magnetite 40%
Chemical Name	Polyethylene Terephthalate Glycol Copolymer filled with Magnetite
Usage	FDM/FFF 3D printing
Diameter	1.75 ± 0.03 mm
Manufacturer	Prusa Polymers a.s., Prague, Czech Republic

Recommended print settings

Nozzle Temperature [°C]	270 ± 5
Heatbed Temperature [°C]	100 ± 10
Print Speed [mm/s]	up to 100
Cooling Fan Speed [%]	10 – 20
Bed Type	satin sheet; powder-coated sheet
Additional Info	The brim is not necessary in general.

Typical material properties

	Typical Value	Method
MFR [g/10 min](1)	N/A	ISO 1133
MVR cm³/10 min	N/A	ISO 1133
Density [g/cm ³]	1.82	ISO 1183
Moisture Absorption in 24 hours [%](2)	0.11	Prusa Polymers
Moisture Absorption in 7 days [%](2)	0.13	Prusa Polymers
Heat Deflection Temperature (0.45 MPa) [°C]	93	ISO 75
Heat Deflection Temperature (1.80 MPa) [°C]	90	ISO 75
Tensile Yield Strength for Filament [MPa]	47.6 ± 0.3	ISO 527
Hardness – Shore D	82 ± 0.4	Prusa Polymers
Interlayer Adhesion [MPa]	13.8 ± 0.6	Prusa Polymers

(1) –

(2) 25 °C; humidity 30 %

Mechanical properties of 3D printed testing specimens(3)

Property\Print Direction	Horizontal	Vertical xz	Method
Tensile Yield Strength [MPa]	45.9 ± 0.6	43.3 ± 0.6	ISO 527-1
Tensile Modulus [GPa]	2.0 ± 0.03	2.0 ± 0.02	ISO 527-1
Elongation at Yield Point [%]	3.9 ± 0.1	3.8 ± 0.1	ISO 527-1
Flexural Strength [MPa]	72.8 ± 2.4	70.3 ± 0.4	ISO 178
Flexural Modulus [GPa]	2.8 ± 0.7	2.5 ± 0.2	ISO 178
Deflection at Flexural Strength [mm]	7.1 ± 0.1	7.2 ± 0.1	ISO 178
Impact Strength Charpy [kJ/m ²](4)	49 ± 4	60.2 ± 12	ISO 179-1
Impact Strength Charpy Notched [kJ/m ²]	4.8 ± 0.2	3.6 ± 0.3	ISO 179-1


(3) Original Prusa i3 MK4S printer was used to make testing specimens. Prusa Slicer 2.8.1 was used to create G-codes with the following settings:

- Prusament PETG Magnetite 40% Filament;
- Print Settings 0.20 mm FAST (layers 0.20 mm);
- Hardened steel nozzle 0.4 mm;
- Solid Layers: Top: 0, Bottom: 0;
- Perimeters: 2;
- Infill: 100% rectilinear;
- Infill Print Speed: 172 mm/s;
- Nozzle Temperature: 265 °C first layer, 270 °C other layers;
- Bed Temperature: 100 °C all layers;
- Extrusion multiplier: 1.05;
- Cooling: 40 – 60 %
- Infill Overlap: 28%

Other parameters are left at default values.

(4) Charpy Unnotched – Edgewise direction of blow according to ISO 179-1

(5) Charpy notched – Edgewise direction of blow according to ISO 179-1

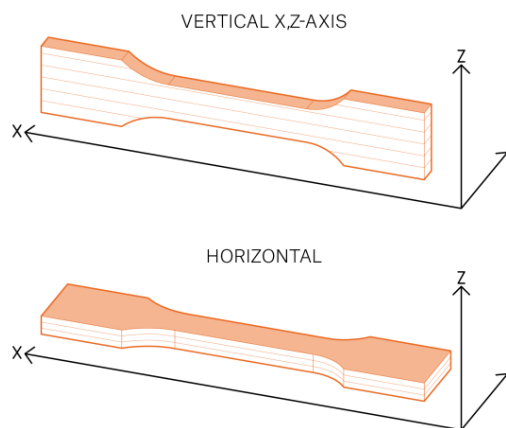

Disclaimer:

The results presented in this data sheet are just for your information and comparison. Values are significantly dependent on print settings, operator experiences, and surrounding conditions. Everyone has to consider suitability and possible consequences of printed parts usage. Prusa Polymers can not carry any responsibility for injuries or any loss caused by using Prusa Polymers material. Before using Prusa Polymers material read properly all the details in the available safety data sheet (SDS).